

EXPERIMENTAL INVESTIGATION TOWARDS THE HIGH PERFORMANCE CONCRETE WITH FRACTIONAL REPLACEMENT OF MOLDING SAND WITH MINERAL ADDITIVES

Dr. S.SRIRAM¹, Assistant Professor, The TIPS SCHOOL OF ARCHITECTURE, Coimbatore, Tamilnadu – 641107.
Mr.D.ARVID², Assistant Professor, The TIPS GLOBAL INSTITUTE, Coimbatore, Tamilnadu – 641107.

Abstract— High performance concrete appears to be a better choice for a strong and durable structure. In this project, investigations were carried out on strength properties such as compressive strength, split tensile strength and flexural strength of M75 grade of HPC mixes with different replacement levels such as 10%, 20%, and 30% of foundry sand with fine aggregate and 10%, 20%, 30% and replacing cement by mineral admixtures such as fly ash and ground granulated blast furnace slag by adopting water-binder ratio of 0.3. Conplast SP430 is based on Sulphonated Napthalene Polymers can be used as a super plasticiser for better workability for high performance concrete. The HPC mix, grade M75 concrete is designed as per ACI 211.4R-08 “Guide for selecting proportions for high strength concrete with Pozzolana Portland cement and other cementitious materials”. Mechanical characteristics like Compressive strength, Split-tensile strength, Flexural strength were examined. The result of these investigations demonstrates the strength characteristics of foundry sand based concrete mixes. Based on the results obtained, the replacement of 30% foundry sand with 3% of super plasticiser which superior strength characteristics was arrived. The details of the investigations along with the results are presented in this report.

Keywords— high performance concrete, high strength, foundry sand, fly ash, ground granulated blast furnace slag

I. INTRODUCTION

HIGH performance concrete (HPC) is a concrete that meets special combinations of performance and uniformity requirements which cannot always be achieved routinely using conventional constituents and normal mixing and placing and curing practises. To produce high performance concrete it is generally essential to use chemical and mineral admixtures in addition to the same ingredients, which are generally used for normal concrete. In recent times, many researches are going on for improving the properties of concrete with respect to strength, durability, and performance as a structural material. There are many materials like fly ash, furnace slag, foundry sand and silica fume etc. One among these special concrete is the foundry sand which is new emerging as one of new generation construction material in producing high strength and

performance concrete for special structures. The interest in fly ash and ground granulated blast furnace slag started in enforcement of air pollution control in many countries. This implies that the industry had to stop releasing fly ash and foundry sand into the atmosphere. To find solution to this problem studies were initiated and after some investigations, it was found that the foundry sand could be used as a very useful material in concrete. Foundry sand in concrete for quite some time in countries like Norway and U.S very high strength concrete is being produced using this fine highly reactive industrial by product. In India, improved Foundry sand and fly ash is finding its use now a day.

II. MATERIALS USED

A. Cement

Portland-Pozzolana cement of grade 53 was used for casting all the specimens should be confirming to IS 1489 (Part 1) : 1991. Portland-pozzolana cement can be produced either by grinding together Portland cement clinker and pozzolana with addition of gypsum or calcium sulphate, or by intimately and uniformly blending Portland cement and fine pozzolana. Portland-pozzolana cement produces less heat of hydration and offers greater resistance to the attack of aggressive waters than normal Portland cement. Moreover, it reduces the leaching of calcium hydroxide liberated during the setting and hydration of cement. Specific gravity and fineness modulus of cement is 3.15 and 7.5 respectively.

B. Fine aggregate

Clean and dry river sand available locally was used. Sand passing through IS 4.75 mm sieve was used for casting all the specimens. Specific gravity and fineness modulus is 2.64 and 2.79 respectively.

C. Coarse aggregate

Coarse aggregate passing through 12.5 mm sieve as given in IS 383 – 1970 was used for all the specimens. In addition to cement paste- aggregate ratio, aggregate type has a great influence on concrete dimensional stability. Specific gravity and fineness modulus is 2.77 and 5.90 respectively.

D. Foundry sand

Foundry sand is high-quality uniform silica sand that is used to make moulds and cores for ferrous and nonferrous metal castings. Foundry sand is a by-product of the castings industry typically comprising uniformly sized sands with various additives and metals associated with the specific casting process. Foundry sand is the most essential raw material and its importance is sometimes forgotten amongst Foundry personnel. Foundry sand is as used by Foundries is desired for its thermal resistance and availability. Most metal casting sand (FS) is high quality silica sand with uniform physical characteristics. Specific gravity of foundry sand is 2.75 and fineness modulus is 2.74

E. Fly Ash (FA)

Fly ash is finely divided residue resulting from the combustion of ground or powered coal. The hardened fly ash concrete shows increased strength together with a lower permeability, where the latter leads to a higher resistance towards aggressive admixtures in addition, partial replacement of cement with fly ash reduces the production cost of concrete due to the lower price of fly ash compared to cement. Class F Fly ash (contains less than 20% lime) is collected from Mettur Thermal Power Plant (MTTP), Mettur. Specific gravity of fly ash 2.30 is and fineness modulus is 7.86.

F. Ground Granulated Blast Slag (GGBS)

Ground Granulated blast furnace slag is a glassy granular material formed when molten blast furnace slag is rapidly chilled, as by immersion in water. The cementations action of a granulated blast furnace slag is dependent to large extent on the glass content. GGBS hydrates are generally found to be more gel like than the products of hydration of Portland cement, so it densifies the cement paste.

G. Super Plasticizer

Super plasticizer CONPLAST SP 430, based on Sulfanated naphthalene polymers, complies with IS 9103-1999 and ASTM C-494 [6] was used.

H. Water

In this project, casting and curing of specimens were done using potable water which shall be free from deleterious materials. Water plays an important role in concrete production (mix) in that it starts the reaction between the cement and the aggregates. It helps in the hydration of the mix.

II. MIX DESIGN

In this investigations concrete mix design (M75) was designed based on ACI 211.4R-1993[7]. This code presents a generally applicable method for selecting mixture proportion for high strength concrete and optimizing this mixture proportion on basis of trial batches. The method is limited to high strength concrete production using conventional materials and production techniques. Mix proportioning details are given below in table 2.

TABLE I
MIX DESIGN

Cement	Fine aggregate	Coarse aggregate	Water
1	1.03	1.973	0.45

Table II
DETAILS OF MIX PROPORTIONS

Mix	Cement Kg/m ³	Foundry sand Kg/m ³	Fly ash Kg/m ³	GGBS Kg/m ³	Fa Kg/m	Ca Kg/m ³
M1	583	0	0	0	601	1151
M2	524.6	60.135	58.34	0	541	1151
M3	466.318	120.27	116.6	0	481	1151
M4	407.977	180.405	175.0	0	420.7	1151
M5	524.6	60.135	0	58.34	541	1151
M6	466.318	120.27	0	116.6	481	1151
M7	407.977	180.405	0	175.0	420.7	1151

III. METHOD OF EXPERIMENT

It is important that the constituent material of concrete remain uniformly distributed within the concrete mass during the various stages of handling and that full compaction is achieved, and making sure that the characteristics of concrete which affect full compaction like consistency, mobility and compatibility are in conformity with relevant codes of practice.

The tests were carried out in accordance with relevant IS Standards. The aggregates were tested for physical properties such as: specific gravity and particle distribution test. The fresh concrete was subjected to the slump test followed by casting of concrete in moulds for further investigations. All the mixes were prepared by mixing the concrete in laboratory mixer along with water and super plasticizer. For compressive strength studies 72 cube specimens of size 150 mm x 150 mm x 150 mm, for flexural strength studies, 72 prism specimens of size 100 mm x 100 mm x 500 mm and 72 cylinder specimens of size 300 mm height and 150 mm

diameter for split tensile strength studies were prepared. All the specimens were cast and cured for 28 days as per standard curing methods

IV. RESULTS AND DISCUSSION

A. Properties of foundry sand and natural sand

Foundry sands consist of green sand and resin sand. Green sands typically comprise of high-quality silica sand, 5-10 % bentonite clay, 2 to 5 % water and less than 5 % sea coal. The green sand process constitutes upwards of 90 % of the moulding materials used.

TABLE III
CHEMICAL PROPERTIES OF FOUNDRY SAND

Compound	Percent by weight
Calcium Oxide (CaO)	0.14
Silicon di Oxide (SiO ₂)	87.91
Aluminum Oxide (Al ₂ O ₃)	4.7
Magnesium Oxide (MgO)	0.30
Phosphorus (P ₂ O ₅)	0.01
Ferric Oxide (Fe ₂ O ₃)	0.94
Potassium Oxide (K ₂ O)	0.25
Sodium Oxide (Na ₂ O)	0.19
Loss on ignition (LOI)	5.15

TABLE IV
PHYSICAL PROPERTIES OF FOUNDRY SAND AND NATURAL SAND

Property	Natural sand	Foundry sand	Test method
Specific gravity	2.64	2.75	IS 2386 (Part III) - 1963
Fineness modulus	2.79	2.74	IS 2386 (Part I) - 1963
Sieve analysis for grading	II	Nearly II	IS 2386 (Part I) – 1963 & IS 383 – 1970

B. Properties of fly ash

TABLE V
CHEMICAL PROPERTIES OF FLY ASH

Compound	Percent by weight
Calcium Oxide (CaO)	18.67
Silicon di Oxide (SiO ₂)	45.98
Aluminum Oxide (Al ₂ O ₃)	23.55
Magnesium Oxide (MgO)	1.54
Potassium Oxide (K ₂ O)	1.80
Sodium Oxide (Na ₂ O)	0.24

TABLE VI
PHYSICAL PROPERTIES OF FLY ASH

Compound	Percent by weight
Calcium Oxide (CaO)	18.67
Silicon di Oxide (SiO ₂)	45.98
Aluminum Oxide (Al ₂ O ₃)	23.55
Magnesium Oxide (MgO)	1.54
Potassium Oxide (K ₂ O)	1.80
Sodium Oxide (Na ₂ O)	0.24

C. Properties of Ground Granulated Blast Slag

TABLE VII
CHEMICAL PROPERTIES OF GROUND GRANULATED BLAST SLAG

Compound	Percent by weight
Calcium Oxide (CaO)	40
Silicon di Oxide (SiO ₂)	35
Aluminum Oxide (Al ₂ O ₃)	16
Magnesium Oxide (MgO)	6
Ferric Oxide (Fe ₂ O ₃)	3

D. Slump test

The slump flow test is used to assess the horizontal free flow of HPC in the absence of obstructions. The test method is based on the conventional slump test. The diameter of the concrete circle is a measure for the filling ability of the concrete. It is the most commonly used test, and gives a good assessment of filling ability. It gives no indication of the ability of the concrete to pass between reinforcement without blocking, but may give some indication of resistance to segregation. The higher the slump flow value, the greater is its ability to fill formwork under its own weight. Acceptable range for HPC is from 50 to 80 mm.

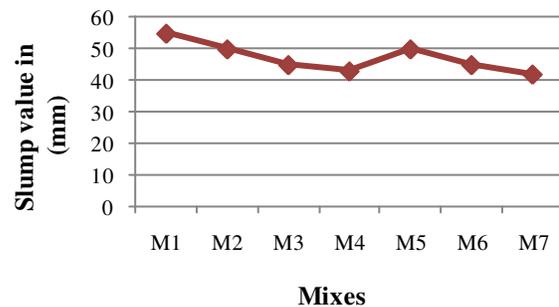


Fig. 1 Slump value for different % of mixes

E. Compressive strength test

Mix	FS by % of FA	FA by % of cement	GGBS by % of cement	Average compressive strength MPa		
				7 days	14 days	28days
M1	0	0	0	35	43	75
M2	10	10	0	37	45	75
M3	15	15	0	37	50	77
M4	20	20	0	42	54	79
M5	10	0	10	45	51	86
M6	15	0	15	43	55	83
M7	20	0	20	41	53	82

M = mega, Pa = pascal, FS = Foundry sand, FA =Fly ash, FA =fine aggregate, GGBS = Ground Granulated Blast Slag

The compressive strength for concrete with replacement of natural sand with foundry sand of 10%, 15%, 20%, and cement by mineral admixtures at the age of 7,14 and 28 days was found as shown in Table VIII and Fig.2.

TABLE VIII
COMPRESSIVE STRENGTH

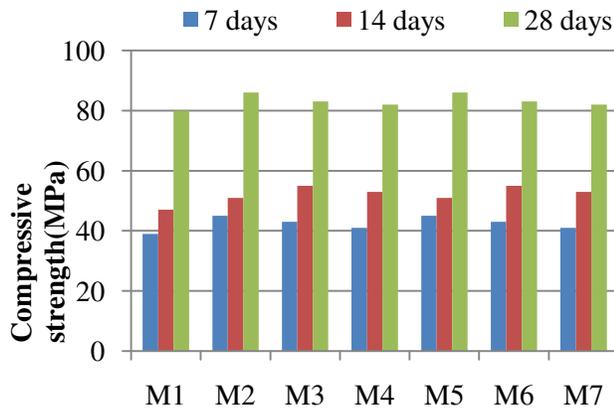


Fig. 2 Comparison of compressive strength for different mixes

The compressive strength continued to increase as the curing period increased. The control mix had a compressive strength of 75MPa at 28 days. Addition of increasing amounts of foundry sand generally increased. The greatest compressive strength was achieved when the mixture contained 30% of fine aggregate replacement of foundry and 10 % addition of Ground Granulated Blast Slag(GGBS) with the water cement ratio 0.3. Improvement stemmed from the void-filling ability of the smaller particles and was more pronounced at lower w/c ratios.

F. Split tensile strength

The split tension test result is shown in Table IX and Fig 3.

It is a method of determining the tensile strength of concrete using a cylinder which splits across the vertical diameter. It is expressed as the minimum tensile stress (force per unit area) needed to split the material apart. We observed that the development of tensile strength of mixes increases as the replacement of natural sand by 10 % of GGBS gives higher strength compared to the control mix.

TABLE IX
SPLIT TENSILE STRENGTH

Mix	FS by % of FA	FA by % of cement	GGBS by % of cement	Average split tensile strength MPa		
				7 days	14 days	28 days
M1	0	0	0	3.345	4.512	6.015
M2	10	10	0	3.445	4.834	6.04
M3	15	15	0	3.3443	4.545	6.0222
M4	20	20	0	3.433	4.656	6.055
M5	10	0	10	3.545	51	6.14
M6	15	0	15	3.533	55	6.1222
M7	20	0	20	3.533	53	6.155

M = mega, Pa = pascal, FS = Foundry sand, FA =Fly ash, FA =fine aggregate, GGBS = Ground Granulated Blast Slag

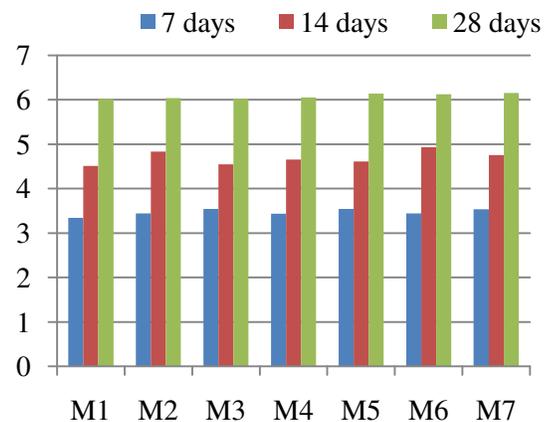


Fig. 3 Comparison of split tensile strength for different mixes

It is a method of determining the tensile strength of concrete using a cylinder which splits across the vertical diameter. It is expressed as the minimum tensile stress (force per unit area) needed to split the material apart. We observed that the development of tensile strength of mixes increases as the replacement of natural sand by 10 % of GGBS gives

higher strength compared to the control mix.

G. Flexural strength test

A beam specimen is casted to test the flexural strength of the concrete. After casting the test specimen it is cured for 7 days and 28 days and tested for maximum load. The result is given the Table X. Fig. 4 shows the variation in flexural strength for different replacement with respect to controlled concrete for 7 days, 14 days and 28 days respectively.

TABLE X
FLEXURAL STRENGTH TEST RESULTS

Mix	FS by % of FA	FA by % of cement	GGBS by % of cement	Average compressive strength MPa		
				7 days	14 days	28 days
M1	0	0	0	3.2	4.5	6.012
M2	10	10	0	3.4	4.5	5.99
M3	15	15	0	3.2	4.6	6.022
M4	20	20	0	3.5	4.7	6.03
M5	10	0	10	3.6	4.8	6.455
M6	15	0	15	3.4	4.9	6.522
M7	20	0	20	3.7	4.6	6.23

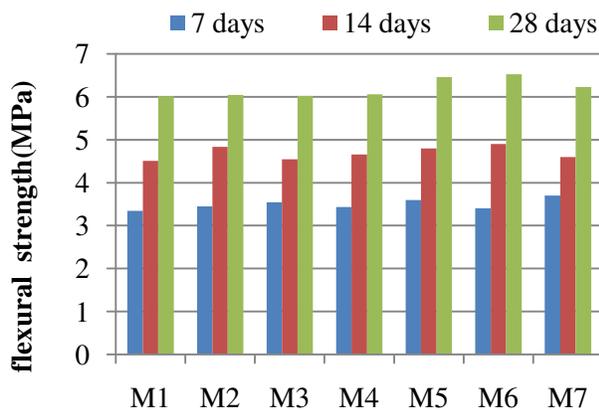


Fig. 4 Comparison of flexural strength for different mixes

The flexural strength continued to increase as the curing period increased. The control mix had a flexural strength of 75MPa at 28 days. Addition of increasing amounts of foundry sand generally increased 20% replacement. The greatest flexural strength was achieved when the mixture contained 30% of fine aggregate replacement of foundry and 20 % addition of Ground Granulated Blast Slag(GGBS) with the water cement ratio 0.3.

H. Discussion

The compressive strength continued to increase as the curing period increased. The control mix had a compressive strength of 75MPa at 28 days. Addition of increasing amounts of foundry sand generally increased. The greatest compressive strength was achieved when the mixture contained 30% of fine aggregate replacement of foundry and 10 % addition of Ground Granulated Blast Slag(GGBS) with the water cement ratio 0.3. Improvement stemmed from the void-filling ability of the smaller particles and was more pronounced at lower w/c ratios. We observed that the development of tensile strength of mixes increases as the replacement of natural sand by foundry sand and 10 % of GGBS gives higher strength compared to the control mix. The flexural strength continued to increase as the curing period increased. The control mix had a flexural strength of 75MPa at 28 days. Addition of increasing amounts of foundry sand generally increased 20% replacement. The greatest flexural strength was achieved when the mixture contained 30% of fine aggregate replacement of foundry and 20 % addition of Ground Granulated Blast Slag(GGBS)

V. CONCLUSION

In this study it has been found that adding optimum superplasticizer dosage the workability is reached. So that the required slump value can be obtained for HPC. The slump value for M75 grade using foundry sand and fly ash is reduced. For 30% fly ash and 30% GGBS replacement, the fresh properties observed were good as compared to 10%, 20% replacement. Hence fly ash replacement is effective for HPC in order to attain high strength. Compare to ordinary concrete M75 grade concrete attain good strength by using lower water/binder ratio. Hence segregation and bleeding occurs in the concrete can be reduced. Foundry sand substitution generally results in favourable outcomes and is highly recommended for all HPC mixes. The strength of concrete structures using foundry sand is always similar to conventional concrete. The presence of foundry sand and mineral admixtures increasing the compressive strength and also withstanding the maximum load. Compare to fly ash GGBS attains good strength as cement replacement.

REFERENCES

[1] ACI Committee 211.4R. (2001), "Guide for selecting proportions for High performance Concrete with Portland Cement and Fly ash", ACI manual of concrete practice.

- [2] ASTM C 494, (1992), "Standard Specifications for Chemical Admixtures for Concrete", Annual Book of American Society for Testing Materials Standards.
- [3] ASTM C 143-03 "Standard Test Method for Slump of Hydraulic Cement Concrete", Annual Book of ASTM Standards, pp. 1-8, 2003.
- [4] BIS: 383-1970 (reaffirmed 1997) "Specification for Coarse and Fine Aggregates from Natural Source for Concrete", New Delhi.
- [5] BIS: 12269-1987 (reaffirmed 1999) "Specification for 53 grade Ordinary Portland Cement", New Delhi. Dushyant Rameshbhai Bhimani, Jayeshkumar Pitroda, Jaydev J. Bhavsar (2010) "used foundry sand: opportunities or development of eco-friendly low cost". International Journal of Emerging Science and Engineering (IJESE) ISSN: 2319-6378, Volume-1, Issue-6, April 2013.
- [6] Er. Magudeaswaran and Dr.Eswaramoorthi(2013) "Experimental Study on Durability Characteristics of High Performance Concrete" Fourth and Final Edition, Pearson Education Limited, Essex Volume 3, Issue 1, January 2013.
- [7] Gambhir M.L, (2005) 'Concrete Technology' Tata McGraw Hill Publications Co.Ltd. New Delhi.
- [8] Gurpreet Singh (2012) "strength and durability studies of concrete containing waste foundry sand" Department of civil engineering Thapar university, patiala-147004 Punjab (india) 2012.
- [9] IS 456 - 2000, "Plain and Reinforced Concrete - Code of Practice" (Third Edition), Bureau of Indian Standards, New Delhi, India.
- [10] IS 383-1970 "Specifications for Coarse and Fine Aggregates from Natural Sources for Concrete," Bureau of Indian Standards, New Delhi, Ninth Reprint, 2006.
- [11] IS 10262-2009 "Concrete Mix Proportioning-Guidelines," Bureau of Indian Standards, New Delhi, First Revision, 2009.
- [12] IS 516-1959 "Methods of Tests for strength of concrete," Bureau of Indian Standards, New Delhi, Eighteenth Reprint, 2006.
- [13] IS 456-2000 "Plain and Reinforced Concrete- Code of Practice," Bureau of Indian Standards, New Delhi, Fifth Reprint, 2002.
- [14] IS 2386 (Part I) – 1963 "Methods of test for aggregates for concrete," Bureau of Indian Standards, New Delhi, Eleventh Reprint, 1997.
- [15] IS 2386 (Part III) – 1963 "Methods of test for aggregates for concrete," Bureau of Indian Standards, New Delhi, Eleventh Reprint, 1997.
- [16] IS 1489 (Part 1) – 1991 "Portland-Pozzolana cement-Specification," Bureau of Indian Standards, New Delhi, First Reprint, 1993.
- [17] Ishatpreet Kaur(2006) "Mechanical properties of concrete incorporating used foundry sand" Department of civil engineering Thapar institute of engineering & technology(deemed university)Patiala – 1470042006.
- [18] Ondovaa.M (2012) "The study of the properties of fly ash based concrete composites with various chemical admixtures".
- [19] Neville A.M.(2002) "Properties of Concrete", Fourth and Final Edition, Pearson Education Limited, Essex. .
- [20] Nath.N,Sarker.P(2011) Department of Civil Engineering, Curtin University, Australia "Effect of Fly Ash on the Durability Properties of High Strength Concrete" The Twelfth East Asia-Pacific Conference on Structural Engineering and Construction .
- [21] Oral buyukoztürk and denvid lau(2000)"High Performance Concrete: Fundamentals and Application" Department of Civil and Environmental Engineering Massachusetts Institute of Technology 77 Mass. Ave., Room 1-280 Cambridge, Massachusetts 02139 .
- [22] Shetty M.S.(2005)"Concrete Technology:Theory and Practice",Revised Edition, S.Chand and Company Ltd.
- [23] Saveria Monosi, Daniela Sani and Francesca Tittarelli (2012) "used foundry sand in cement mortars and concrete production" The Open Waste Management Journal, 2010, 3, 18-25.
- [24] S.Keerthinarayana and R. Srinivasan (2010) "study on strength and durability of concrete by partial replacement of fine aggregate using crushed spent fire bricks".
- [25] Siddique, Schutter, G, Noumowe. A (2009) "the effect of waste foundry sand (WFS) as partial replacement of fine aggregate on the compressive strength and modulus of elasticity of concrete. Construction and Building Materials 2009; 23: 976-980.
- [26] Toutanji.H "Effect of supplementary cementitious materials on the compressive strength and durability of short-term cured concrete" Cement and Concrete Research, vol 34, pp 311 – 319, 2003.